

# Tenaris TEMPALOY AA-1



# Tenaris

Tubular technologies. Innovative services.

Tenaris is the leading global manufacturer and supplier of tubular products and services used in the drilling, completion and production of oil and gas and a major supplier of tubular products and services used in process and power plants and in specialised industrial and automotive applications.

Through our integrated global network of manufacturing, R&D and service facilities, we are working with our customers to meet their needs for the timely supply of high performance products in increasingly complex operating environments.



# Technical datasheet of Tenaris TEMPALLOY AA-1



## Introduction

Tenaris's TEMPALLOY AA-1 is a 18Cr-10Ni-3Cu-Ti-Nb-B austenitic stainless steel developed for boiler construction, in particular for the fabrication of superheaters and reheaters.

Its specific chemical composition, developed and tailored by TenarisNKK Tubes, produces a steel with extremely high creep and corrosion resistance. This is a key requirement for advanced materials used for supercritical and ultra-supercritical boilers.

Tenaris's TEMPALLOY AA-1 is suitable for applications with steam temperatures up to 650°C (1202°F).

TEMPALLOY AA-1 tubes are produced for Tenaris by Sanyo Special Steel Co. Ltd. in Japan.

## Key features

- 18Cr-10Ni austenitic stainless steel with addition of 3%Cu, Nb, Ti and B to maximise creep strength
- Excellent and long-term stable creep properties up to 750 °C (1382 °F)
- High oxidation and corrosion resistance at elevated temperatures
- Possibility to perform internal shot-blasting to further increase steam oxidation resistance
- Maximum design temperature is 750 °C (1382 °F) according to ASME Code Case 2512
- Balanced chemical composition to avoid embrittlement after long term high temperature exposure.

## Applicable international codes and standards

- ASTM A213 S30434
- ASME Code Case 2512
- METI SUS321J2HTB
- VdTÜV-Werkstoffblatt 564/2
- EN 10216-5 application pending

## Chemical composition, microstructure and mechanical properties

The chemical composition, as specified by ASTM A213 and ASME Code Case 2512, is reported in Table 1. Table 2 reports the minimum mechanical properties required by ASTM and ASME codes.

The level of Cr and Ni confers a stable austenitic structure free from  $\delta$ -ferrite, as shown in fig. 1. The addition of Nb and Ti promotes the formation of fine MX type precipitates, besides Cr-rich  $M_{23}C_6$ .

Through the addition of Cu, a coherent Cu-rich phase precipitates, increasing significantly the creep resistance of the steel.

The studies performed by the R&D centre of TENARIS NKK Tubes showed that an addition of 3% of Cu guarantees a significant increase of creep strength of the material (Fig.2). The microstructure obtained is very stable, as confirmed by the long term creep and ageing tests performed on TEMPALLOY AA-1 (Fig. 5).

Not only the creep performance of TEMPALLOY AA-1 are outstanding, but this steel maintains also a high toughness after long exposure at service temperature. After ageing tests performed between 650 °C and 750 °C up to 10000h, TEMPALLOY AA-1 shows impact values always above 100J/cm<sup>2</sup>.

The heat treatment consists of a solution annealing at a temperature above 1160 °C (2120 °F) followed by rapid cooling in water or in other medium.

The heat treatment temperature range has been optimised to maximise the long term creep properties by promoting a fine and diffuse precipitation of MX carbides during exposure at service temperature.

## TEMPALLOY AA-1 - CHEMICAL COMPOSITION

TEMPALLOYAA-1	C*	Mn	P	S	Si	Cr	Ni	Nb*	Ti*	B	Cu
Min	0.07	-	-	-	-	17.5	9.0	0.10	0.10	0.001	2.50
Max	0.14	2.00	0.040	0.010	1.00	19.5	12.0	0.40	0.25	0.004	3.50

Table 1 - Chemical composition according to ASTM A213 and ASME codes  
\* 2.0<(Ti+Nb)/C<4.0



Fig.1 Microstructure of a tube ODxWT 50.8x10.3mm  
Left: Optical Microscope; Right: Transmission Electronic Microscope

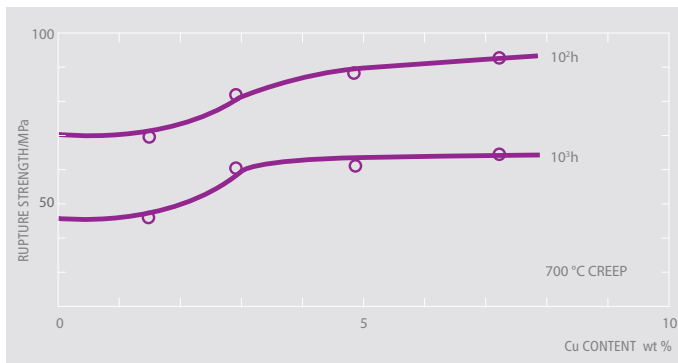


Fig. 2 – Effect of Cu on creep strength

MECHANICAL PROPERTIES		
YS, min	205 MPa	30 ksi
UTS, min	500 MPa	73 ksi
Elongation in 2", min	35%	

Table 2 – Mechanical properties at room temperature, as specified by ASTM A213

### Creep properties and allowable stresses

TEMPALOY AA-1 has been extensively characterised regarding creep properties. Creep tests have been performed at 600, 650, 700, 750 and 800°C at different stresses with test durations also longer than 10<sup>5</sup>h and with more than 1.5 million broken creep test hours. The ECCC (European Creep Collaborative Committee) guidelines have been followed for the assessment and PATs (Post-Assessment-Tests) have been successfully passed, confirming the quality and the consistency of the results. The assessed values are reported in Table 3.

AVERAGE CREEP RUPTURE STRESSES						
TEMPERATURES (°C)	Stress (MPa) at Duration (h)					
	100	10000	30000	100000	150000	*200000
550	442	321	294	266	256	250
560	423	303	277	249	240	234
570	406	287	261	234	225	219
580	388	271	245	218	209	204
590	371	255	230	204	195	189
600	355	240	215	189	181	175
610	338	225	201	175	167	162
620	323	211	187	162	155	149
630	307	197	174	150	142	137
640	292	184	161	137	130	125
650	277	171	149	126	119	114
660	263	158	137	115	108	104
670	249	146	126	105	98	94
680	235	135	115	95	89	84
690	222	124	105	86	80	76
700	209	114	95	77	72	68
710	197	104	86	69	64	61
720	185	94	78	62	57	54
730	173	86	70	55	51	48
740	161	78	63	49	45	43
750	151	70	56	44	40	38

Table 3 – Assessed average creep rupture strength. The lower scatter band is usually defined as the 80% of the average creep strength

\* Extrapolation at 200000 h not covered by PATs

The allowable stresses for the design according ASME rules are given in ASME code case 2512. The values are reported in Table 4.

ALLOWABLE STRESSES					
Metal Temperature Not Exceeding [°C]	Allowable Stress Values [MPa]	Allowable Stress Values [MPa]	Metal Temperature Not Exceeding [°C]	Allowable Stress Values [MPa]	Allowable Stress Values [MPa]
-30 to 40	138	138	425	105	138 *
65	126	138 *	450	102	137 *
100	121	138 *	475	99.7	135 *
125	118	138 *	500	97.1	131 *
150	117	138 *	525	94.5	128 *
175	116	138 *	550	92.2	124 *
200	116	138 *	575	90.0	122 *
225	116	138 *	600	88.2	119 *
250	116	138 *	625	86.6	102 *
275	115	138 *	650	80.7	80.7
300	114	138 *	675	63.3	63.3
325	113	138 *	700	50.5	50.5
350	111	138 *	725	41.5	41.5
375	109	138 *	750	35.2	35.2
400	107	138 *			

Table 4 - Allowable stresses from ASME code case 2512 (table 3M)

GENERAL NOTE: The revised criterion of 3.5 on tensile strength was used in establishing these values.

NOTE: (\*) Due to the relatively low yield strength of this material, these high stress values were established at temperatures where the short-time tensile properties govern to permit the use of these alloys where slightly greater deformation is acceptable. These higher stress values exceed 66 2/3%, but do not exceed 90% of the yield strength at temperature. Use of these stresses may result in dimensional changes due to permanent strain. These stress values are not recommended for the flanges of gasketed joints or other applications where slight amounts of distortion can cause leakage or malfunction. (From ASME code Case 2512)

## Physical properties

The main physical properties have been measured and are reported in Table 5.

PHYSICAL PROPERTIES			
T [°C]	Cp [J/g*°C]	k [W/(mK)]	[10 <sup>-6</sup> /K] *
25	0,4552	14,75541	-
50	0,4602	14,97312	17,9
100	0,4702	15,47386	18,0
200	0,4902	16,63865	18,5
300	0,5102	17,92392	18,85
400	0,5302	19,27374	19,1
500	0,5502	20,66138	19,2
550	0,5602	21,36465	19,2
600	0,5702	22,07259	19,3
650	0,5802	22,97524	19,5
700	0,5902	23,86783	19,6
750	0,6002	24,22722	19,7
800	0,6102	24,53322	19,8

Table 5 – Main physical properties of TEMPALLOY AA-1 (Tenaris data)

\* Measured between 20 °C and the reference temperature

## Steam oxidation and corrosion resistance

High temperature corrosion and steam oxidation resistance are key-parameters for the selection of boiler materials.

Specific tests were performed on TEMPALLOY AA-1 to evaluate the corrosion resistance in simulated coal ash and heavy oil combustion atmospheres.

The results achieved show good corrosion resistance thanks to its high Cr content. Steam oxidation properties have also been evaluated at different temperatures.

The results of laboratory steam oxidation tests performed at different temperatures for 1000h are reported in Fig. 3 compared with the benchmark material, a type 321H stainless steel.

The optional shot-blasting operation on the inner tube surface increases significantly the steam oxidation resistance.

The cold working caused by the shot-blasting promotes a fast diffusion of Cr towards the inside surface, increasing locally the Cr concentration and consequently the oxidation resistance.

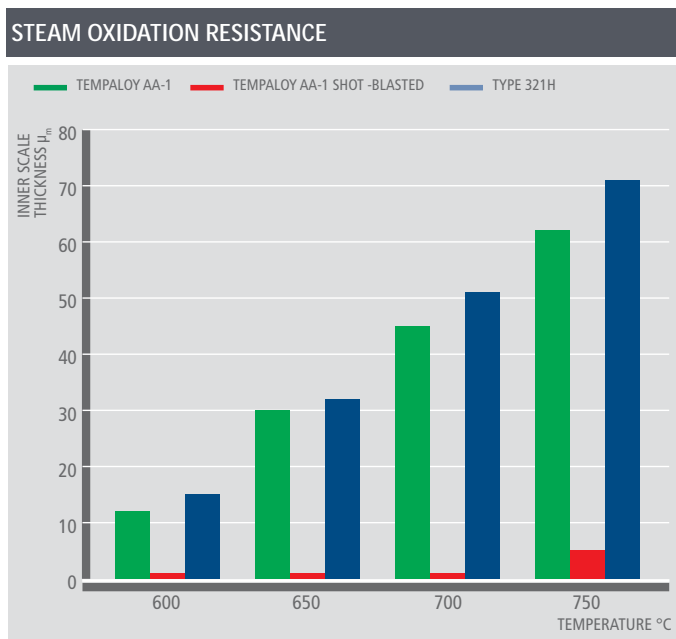


Fig. 3 - Steam oxidation of TEMPALLOY AA-1 in standard and shot-blasted condition

## Cold forming of TEMPALLOY AA-1 tubes

Rules for heat treatment of cold bent TEMPALLOY AA-1 tubes are given by ASME 2007 Section 1 PG-19.

If the finishing-forming temperature is below 1160 °C (2120 °F) or if percentage strain calculated as:

$$\% \text{ strain} = \frac{100 r}{R}$$

(where r is the nominal radius of the tube and R the bending radius) exceeds the values indicated in table 6, a solubilization heat treatment is necessary

The soaking time shall be 20 minutes per inch of thickness or 10 minutes, whichever is greater.

The minimum solubilization temperature shall be 1160 °C (2120 °F), while the maximum temperature shall be 1245 °C (2270 °F).

## SOLUBILIZATION HT AFTER BENDING

Limitations in lower temperature range		Forming strain exceeding	Limitations in higher temperature range		Minimum heat treatment temperature when design temperature and forming strains are exceeded		
For design temperature Exceeding	But less than or equal to		For design temperature exceeding	Forming strain exceeding			
°F	°C	°F	°C	°F	°C		
1000	540	1250	675	15% *	10%	2120	1160

\*: for simple bends of tube and pipes whose outside diameter is less than 3.5 in. (89mm), this limit is 20%

Table 6 – Rules for heat treatment of cold bent TEMPALLOY AA-1 tubes, from ASME 2007 Section 1 PG-19.

## Welding

TEMPALOY AA-1 tubes can be welded without pre-heating and PWHT. Specific similar welding consumables for GTAW and SMAW processes have been developed by Kobelco and are currently available on the market as TG-S1AS and NC-B1AS respectively

The use of approved fillers guarantees optimum welding results and enhanced creep resistance of the welded joints.

Creep tests on cross welded joints produced with Kobelco welding consumables show a creep resistance of the welded joint perfectly in line with that of base material (Fig. 5)

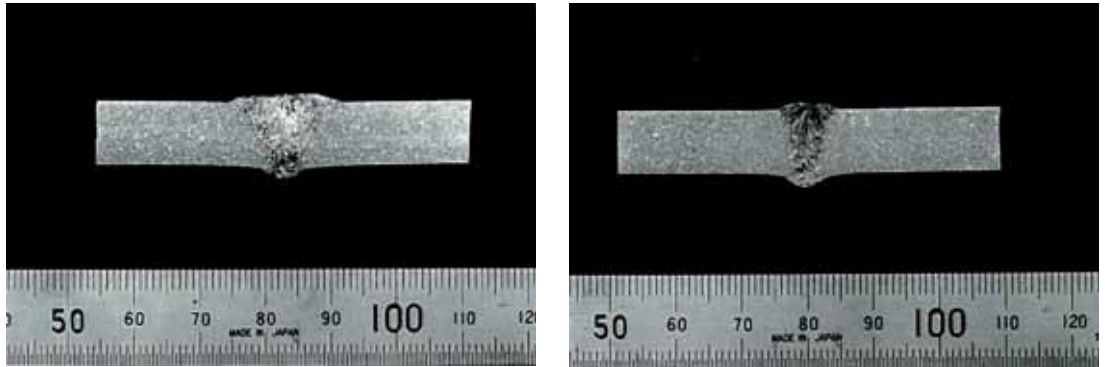


Fig. 4 – Macro sections of welded joints manufactured by GTAW process (left) and GTAW+SMAW (right)

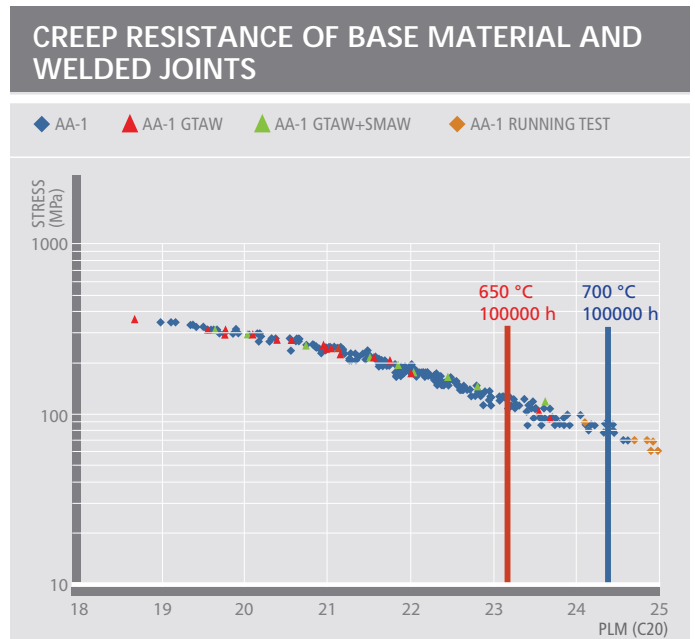


Fig. 5 – Tenaris creep data for TEMPALOY AA-1 base material and cross weld joints



## CONTACT US

James Marsden  
Power Generation Business Unit  
Manager  
jmarsden@tenaris.com  
(39) 35 5602850 tel

**MARKETING**  
Stefano Caminada  
Technical Sales Support  
scaminada@tenaris.com  
(39) 35 560 2833 tel

Nicola Pedrinelli  
Marketing Intelligence  
npedrinelli@tenaris.com  
(39) 35 560 2429 tel

Silvia Carestia  
Marketing Communications  
scarestia@tenaris.com  
(39) 35 560 3255 tel

**PRODUCT DEVELOPMENT**  
Giuseppe Cumino  
Power generation Manager  
gcumino@tenaris.com  
(39) 35 560 2865 tel

[www.tenaris.com](http://www.tenaris.com)

**AMERICAS**  
George Kubove  
gkubove@tenaris.com  
(1) 713 3367325 tel

**NORTH EUROPE**  
Edgar Villanova  
evillanova@tenaris.com  
(49) 89 232375111 tel

**SCANDINAVIA**  
John Shine  
jshine@tenaris.com  
(44) 207 291 0200 tel

**EASTERN EUROPE**  
Mihai Muresan  
mmuresan@tenaris.com  
(49) 89 232375112 tel

**SOUTH EUROPE**  
Marco Innocenti  
minnocenti@tenaris.com  
(39) 35 560 2852 tel

**INDIA**  
Sharma Avneesh  
asharma@suppliers.tenaris.com  
(44) 4263 4408/9 tel

**KOREA**  
Shin Kwang Ki  
kkshin@tenaris.com  
(82) 2 798 3385 tel

**SINGAPORE**  
Judy Cheung  
jcheung@tenaris.com  
(86) 13 80109 8921 tel

**JAPAN**  
Olivier Couette  
ocouette@tenaris.com  
(82) 2 3781 0200 tel